



## Product Brochure

Neodymium YAG

### Information about our Nd:YAG laser crystal products

- [Laser Rod Specifications](#)
- [Ordering Information](#)

### Information about Nd:YAG & crystal growth

- [Nd:YAG Production at LMC](#)
- [Notes about Nd Concentration](#)
- [Properties of Nd:YAG](#)



---

*For more information, visit our web site*  
<http://www.LaserMaterials.com>

# Nd:YAG Production

*Laser Materials Corporation produces Nd:YAG boules, fabricated laser rods and slabs. Our crystal growth facility in Vancouver, Washington exclusively produces large diameter boules (currently, Ø82 mm) in lengths up to 250 mm while retaining acceptable Neodymium concentration levels. As a crystal grower, we concentrate on developing and improving the crystal growth process to produce high yields and consistently high material quality. Pure raw materials, precise formulation, and exacting growth control are the keystones of our operations.*




*Ø75 x 208 mm boule section  
(Nd:YAG, 1.1 atom % Nd concentration)*



- Better than 99.997% pure yttrium and aluminum oxides, and 99.99% pure neodymium oxide are used.
- 99.999% pure or better shield gases are used throughout the crystal growth process.
- All raw materials are stored and prepared in a clean environment.
- Constituent powders are thoroughly dried in high temperature ovens to reduce hydroxyl impurities.
- The dried raw materials are carefully weighed on precision balances to insure precise stoichiometry and dopant concentration.
- Computer control of the growth process and associated facilities produces the stable conditions required for consistent boule growth; cooling water and room air temperatures are maintained to within closely controlled tolerances.
- Crystal growth control is based on weight gain for the most consistent boule diameter possible.

Laser rod "blanks" are extracted from completed boules using a diamond core drill; for slabs, a slicing saw is used to cut out the rough rectangular shape. In either case, the rough finished blanks are then sent out for the finishing operations of precision grinding to final size, polishing, and anti-reflection coating. You have the option of purchasing finished rods directly from us or purchasing unfinished "blanks" and using the fabricator of your choice.

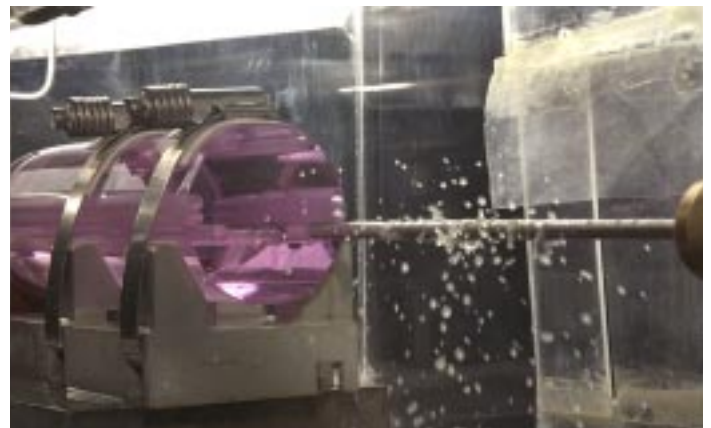

*core drilling a Ø5 mm rod from a  
Ø75 x 208 mm boule section*

# Nd:YAG Crystal Growth

*Growth of neodymium doped yttrium aluminum garnet (Nd:YAG) crystals by the Czochralski technique is the method of choice for virtually all commercially available Nd:YAG. This is a time consuming process requiring careful control of the growth environment over a period of 4 to 5 weeks just to produce one crystal boule. Still, the Czochralski method has proven to be the only acceptable way to produce Nd:YAG with sufficient optical clarity and homogeneity for use in a laser system.*

## Crystal quality Vs. Boule size

One of the most important advances in Nd:YAG production in recent years has been the trend toward larger diameter boules. Internal strain in the grown boule is the principle cause of optical distortion in finished laser rods more than a few tens of millimeters in length (in shorter rods, the quality of the end finish is more important). Larger boules have significantly lower strain levels over much of their cross section resulting in significantly lower optical distortion in finished rods.

An additional advantage of larger boules is reduced cost. The cross-sectional area is increased while the linear growth rate remains comparable, resulting in an increased rate of material growth. At large diameters, Nd:YAG is more sensitive to process parameter fluctuations and obtaining high yields of good product is more difficult. But as a result of improved control electronics and computerization of the growth process, growth rate fluctuations can be maintained well within tolerance to provide high yields of good product at large diameter.



## Neodymium Concentration

In neodymium doped yttrium aluminum garnet, neodymium substitutes for yttrium in the crystal lattice. However, because neodymium is larger than yttrium, this substitution does not occur readily. In fact, the concentration of neodymium in the crystal is only a small fraction of its concentration in the melt. Since the growing crystal is continually rejecting neodymium, the concentration of the melt (and hence the crystal) increases as the growth progresses. To minimize this effect it is necessary to use a large crucible and to pull only a small fraction (typically 20-30%) of the total material available. The upper graph shows how the concentration of neodymium increases as a function of melt fraction pulled.

At Laser Materials Corporation, we grow boules at two average Nd concentrations: 0.80% Nd and 1.10% Nd. The Nd concentration profile for each is illustrated in the lower graph. The composition is engineered to provide the specified average concentration in 200 mm lengths. Lengths up to 250 mm can be provided with slightly higher average Nd concentrations.

For material less than 200 mm, the average concentration will vary depending on from where in the boule the material is cut. Each individual laser rod we ship is supplied with data including the average Nd concentration and the change in concentration over the rod's length. Standard tolerances for various rod lengths are listed on our laser rod specification sheet.

It should be noted that the absolute accuracy of the neodymium concentration must take into how accurately the distribution coefficient (ratio of dopant concentration in the crystal to that in the melt) is known. At Laser Materials Corporation our formulations are based on a value of 0.18, which is consistent with industry practice and most determinations in the literature.

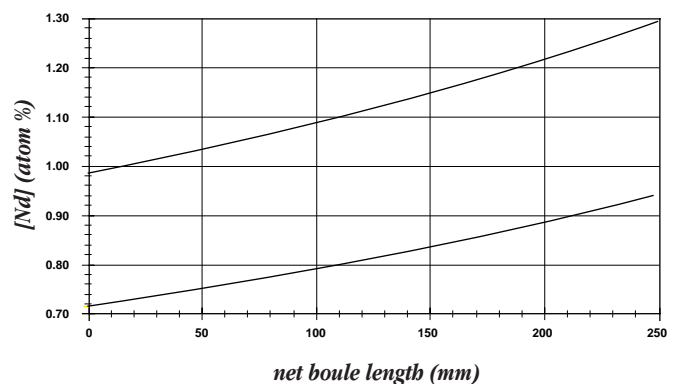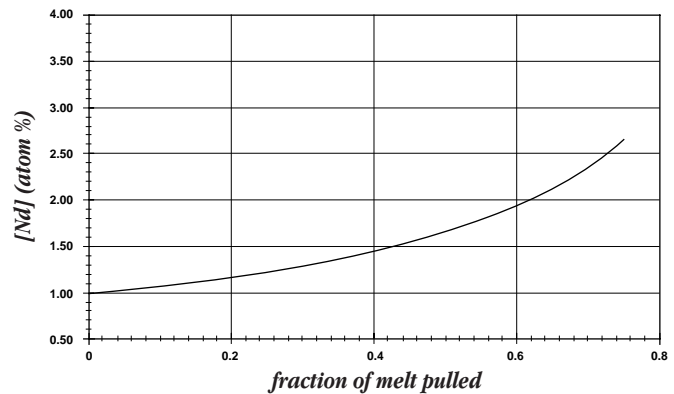

# Nd:YAG Material Properties

## Chemical/Physical

Chemical Formula	$Y_{2.97}Nd_{0.03}Al_5O_{12}$
Formula Weight	595.3 g·mole <sup>-1</sup>
Crystal System/Structure	Cubic/Garnet
Space Group	$O_h^{10}$ -Ia3d
Lattice Constant	12.01 Å
Melting Point	1950 ±20 °C
Density	4.55 g·cm <sup>-3</sup>
Hardness (Knoop)	1350 ±35 kg·mm <sup>-2</sup>

## Mechanical

Modulus of Elasticity (E)	310 GPa (45 x 10 <sup>6</sup> psi)
Poisson's Ratio (ν)	0.3
Tensile Strength (σ <sub>t</sub> )	175-200 MPa (25-30 x 10 <sup>3</sup> psi)

## Thermal

Specific Heat Capacity (C <sub>p</sub> )	0.59 J·g <sup>-1</sup> ·K <sup>-1</sup>
Thermal Conductivity (k)	0.13 W·cm <sup>-1</sup> ·K <sup>-1</sup>
Thermal Expansion Coef. (α)	7 x 10 <sup>-6</sup> K <sup>-1</sup>
Thermal Shock Parameter (R)	7-8 W·cm <sup>-1</sup>

From the Thermal Shock Parameter, the fracture limit for thermal dissipation in a CW laser rod can be calculated:

For rods it is independent of rod diameter (= 8πR) 175-200 W·cm<sup>-1</sup>

For slabs it is dependent on the aspect ratio (= 12R·W/t).

For a 4:1 aspect ratio (=48R) 330-390 W·cm<sup>-1</sup>

Note: These values are absolute maxima and can be greatly affected by surface finish, fixturing, etc.

## Optical

Refractive Index (n)	1.818 at 1.064 μm
Temperature Coef. (dn/dT)	9.05 x 10 <sup>-6</sup> K <sup>-1</sup>
Wavelength Dependence:	
0.80 μm	1.8245
0.90 μm	1.8222
1.00 μm	1.8197
1.10 μm	1.8170
1.20 μm	1.8152
Elasto-optic Coefficients:	
P <sub>11</sub>	-0.029
P <sub>12</sub>	0.0091
P <sub>44</sub>	-0.0615

## Laser/Spectroscopic

Lasing System	Four Level
Lasing Upper State	<sup>4</sup> F <sub>3/2</sub>
Fluorescent Lifetime	230 μs
Main Pump Bands	0.75 & 0.81 μm

### <sup>4</sup>F<sub>3/2</sub> → <sup>4</sup>I<sub>11/2</sub> Stark Level Transitions:

Transition	Wavelength (μm)	Relative Laser Performance
R <sub>2</sub> → Y <sub>1</sub>	1.05205	46
R <sub>1</sub> → Y <sub>1</sub>	1.06152	92
R <sub>2</sub> → Y <sub>3</sub>	1.06414	100 (Principle)
R <sub>1</sub> → Y <sub>2</sub>	1.0646	50
R <sub>1</sub> → Y <sub>3</sub>	1.0738	65
R <sub>1</sub> → Y <sub>4</sub>	1.0780	34
R <sub>2</sub> → Y <sub>5</sub>	1.1054	9
R <sub>2</sub> → Y <sub>6</sub>	1.1121	49
R <sub>1</sub> → Y <sub>5</sub>	1.1159	46
R <sub>1</sub> → Y <sub>6</sub>	1.12267	40

### <sup>4</sup>F<sub>3/2</sub> → <sup>4</sup>I<sub>13/2</sub> Stark Level Transitions:

Transition	Wavelength (μm)	Relative Laser Performance
R <sub>2</sub> → X <sub>1</sub>	1.3188	34
R <sub>2</sub> → X <sub>2</sub>	1.3200	9
R <sub>1</sub> → X <sub>1</sub>	1.3338	13
R <sub>1</sub> → X <sub>2</sub>	1.3350	15
R <sub>2</sub> → X <sub>3</sub>	1.3382	24
R <sub>2</sub> → X <sub>4</sub>	1.3410	9
R <sub>1</sub> → X <sub>4</sub>	1.3564	14
R <sub>2</sub> → X <sub>6</sub>	1.4140	1
R <sub>1</sub> → X <sub>7</sub>	1.4440	0.2

Unless otherwise noted, data is for 1% Nd (atomic) at 300K. For more information, consult the following references from which the above data was compiled.

Walter Koechner, *Solid-State Laser Engineering-Third Completely Revised and Updated Edition* (Springer-Verlag, Berlin, Heidelberg 1992)

Alexander A. Kaminskii, *Laser Crystals-Their Physics and Properties, Second Edition* (Springer-Verlag, Berlin, Heidelberg, 1990)

*CRC Handbook of Laser Science and Technology, Volume V, Optical Materials, Part 3: Applications, Coatings, and Fabrication*, Marvin J. Weber Ed. (CRC Press, Boca Raton, FL 1987)

12706 NE 95<sup>th</sup> St., #102  
Vancouver WA 98682  
U.S.A.

Tel.: (360) 254-4180


FAX: (360) 254-4182

web: [www.LaserMaterials.com](http://www.LaserMaterials.com)

e-mail: [hq@LaserMaterials.com](mailto:hq@LaserMaterials.com)

**LASER**  
**MATERIALS**  
CORPORATION

# Nd:YAG Laser Rods

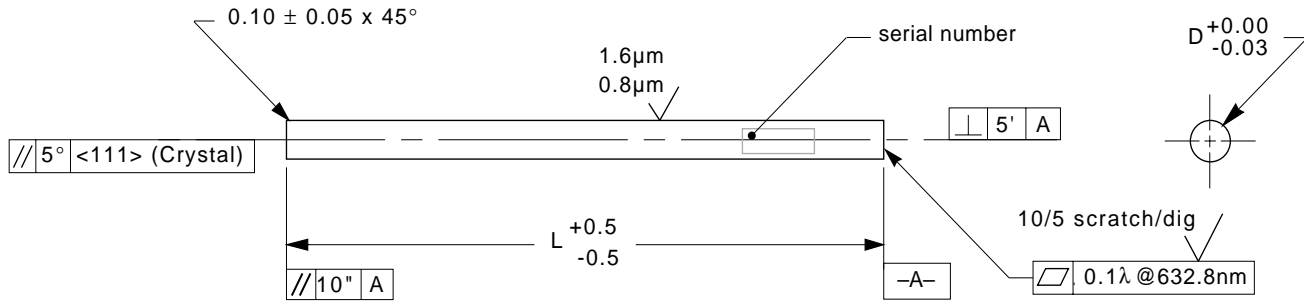


## Revised specifications effective 30-April-2001

L mm	D mm	Standard Grade		Premium Grade		Standard [Nd]=1.1 Atom%		Low [Nd]=0.8 Atom%	
		Extinc. Ratio (dB)	Wave. Error (λ)	Extinc. Ratio (dB)	Wave. Error (λ)	Tolerance of Average [Nd]	Δ[Nd] Over Rod Length	Tolerance of Average [Nd]	Δ[Nd] Over Rod Length
50	3	>25	<.19	>30	<.13	±.08	0.06	±.07	0.05
50	4		<.21		<.15				
50	5		<.24		<.16				
65	3	>24	<.20	>29	<.14	±.08	0.08	±.07	0.06
60	4		<.22		<.15				
65	5		<.26		<.17				
75	3	>23	<.21	>28	<.15	±.08	0.10	±.07	0.07
75	4		<.24		<.17				
75	5		<.28		<.18				
75	6		<.31		<.20				
75	6.35		<.32		<.21				
75	8	<.38	<.24						
100	4	>22	<.28	>27	<.18	±.08	0.13	±.06	0.09
100	5		<.32		<.21				
100	6		<.36		<.23				
100	6.35		<.37		<.24				
100	8		<.44		<.28				
125	5	>21	<.36	>26	<.23	±.07	0.16	±.05	0.11
125	6		<.41		<.26				
125	6.35		<.43		<.27				
125	8		<.51		<.31				
125	9.53		<.59		<.36				
150	6.35	>20	<.48	>25	<.30	±.05	0.18	±.04	0.13
150	8		<.58		<.35				
150	9.53		<.67		<.40				
200	8	>19	<.71	>24	<.42	±.02	0.23	±.02	0.17
200	9.53		<.82		<.49				
200	10		<.86		<.51				
250	8	>18	<.84	>23	<.50	±.03	0.31	±.03	0.22
250	9.53		<.98		<.57				
250	10		<1.03		<.60				

## Coatings


Type	Reflectivity %R per Surface	Damage Threshold (20nS Pulse, GW·cm <sup>-2</sup> )	Damage Threshold (CW, kW·cm <sup>-2</sup> )
AR @1064nm	<0.15	>1.4	>25
HR @1064nm	>99.9	>1.0	>25
Partially Reflecting	95 to 99 ± 0.5	>1.0	>25
Partially Reflecting	90 to 95 ± 1	>1.0	>25
Partially Reflecting	10 to 90 ± 3	>1.0	>25

# Ordering Information

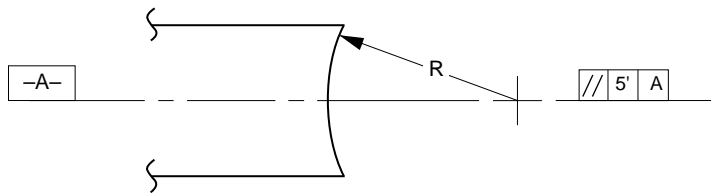

## Radiused End


R (m)  
 0.5±.05  
 1.0±.1  
 2.0±.2  
 3.0±.3  
 5.0±.5  
 10±1

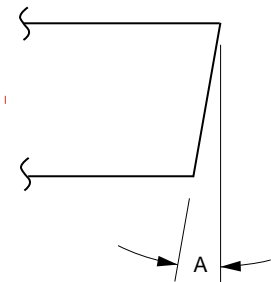

## Wedged End

A  
 30' ± 10'  
 1° ± 10'  
 2° ± 10'  
 6° ± 10'  
 8° ± 10'

Note: if both ends wedged parallel,  
 A-B angle < 10"

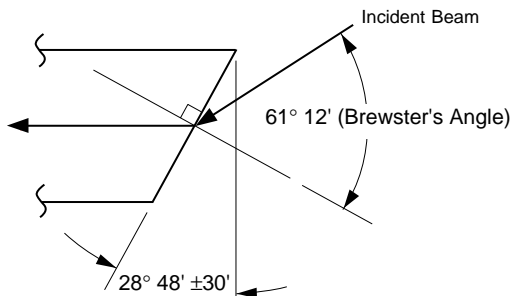

## Brewster End

% Reflectivity = .06% for plane polarized incident beam at limit of angle tolerance.

## Part Numbering

[Atom % Nd]NY[P] - [Diameter (mm)] - [Length (mm)] - [A-End/B-End] - [A-Coating/B-Coating]

0.80% --- 08      Premium --- P  
 1.10% --- 11      Standard --- Blank

Note: Indicate anti-parallel wedged ends by a negative angle on one end

Flat ----- F	Anti Reflection ----- A
Radiused -- R+Radius	High Reflection ----- H
Wedged --- W+Angle	Partial Reflection ---- P(%R)
Brewster -- B	None ----- N
Special ---- S	
Unfinished N	

Example:

08NY-6.35-100-W1/W1-A/A

Designates 0.08% standard grade Nd:YAG , D=6.35mm L=100 mm, both ends angled 1° parallel, and an AR coating on both ends.

To request a quote, you can call or FAX us with your requirements at the numbers below. Or, click this hyperlink to go to an online [quote request form](#) at the Laser Materials Corporation web site.



12706 NE 95<sup>th</sup> St., #102  
 Vancouver WA 98682  
 U.S.A.

Tel.: (360) 254-4180

FAX: (360) 254-4182

web: [www.LaserMaterials.com](http://www.LaserMaterials.com)

e-mail: [sales@LaserMaterials.com](mailto:sales@LaserMaterials.com)